

# Recombinant Human Bone Morphogenetic Protein-2 Stimulates the Osteogenic Potential of the Schneiderian Membrane: A Histometric Analysis in Rabbits

Youna Choi, MSD,\* Jung-Seok Lee, MSD,\* Yu-Jin Kim, MSD, Min-Soo Kim, MSD, Seong-Ho Choi, PhD, Kyoo-Sung Cho, PhD, and Ui-Won Jung, PhD

This study evaluated the osteoinductive effect of the recombinant human bone morphogenetic protein-2 (rhBMP-2)-coated biphasic calcium phosphate (BCP) carrier system on the grafted sinus area, including surrounding tissues and the Schneiderian membrane. A total of 18 male rabbits were used in this study; two for *in vitro* and 16 for *in vivo* experiments. Schneiderian membranes taken from two animals were cultured with or without rhBMP-2, and quantitative reverse transcriptase-polymerase chain reaction analysis was performed. Both maxillary sinuses in each of the 16 animals were used to compare the *in vivo* effects of rhBMP-2-coated BCP (experimental group) and BCP alone (control group). In each animal, rhBMP-2-coated BCP was grafted into one of the maxillary sinuses, and the same amount of BCP alone was grafted into the contralateral site in random order. Radiologic and histometric analyses were performed at 2 and 8 weeks after surgery. After 2 days of culturing with or without rhBMP-2, a significant increase in the expression of early osteoblasts (*RUNX2*, type I collagen, alkaline phosphatase, and osteopontin) could be observed. Different histologic healing patterns were observed in experimental and control sites: newly formed bone lining the reflected sinus membrane without bone formation was observed at the central areas of experimental sites (window = 0.06%; center = 0%; membrane = 20.86% of new bone), whereas evenly distributed new bone formation was observed at the control sites (window = 7.27%; center = 7.41%; membrane = 15.58% of new bone). The augmented volume was well maintained at both the experimental and control sites during the experimental period, but at 2 weeks, the augmented volume was greater at the experimental sites than at the control sites (232.62 and 195.29 mm<sup>3</sup>, respectively;  $p < 0.001$ ). These results suggest that good space maintenance in sinus augmentation is achieved with BCP, while the osteoinductive potential of the sinus membrane is activated at the early stage of healing with rhBMP-2.

## Introduction

QUANTITATIVELY AND QUALITATIVELY successful vertical augmentation for dental implants has been achieved in severely resorbed posterior maxillae using sinus floor elevation combined with bone grafting.<sup>1-3</sup> Several systematic reviews have confirmed predictable long-term clinical results for maxillary sinus grafts, which could be attributed to the development of superior bone substitutes, rough-surfaced implants, and improved surgical skills.<sup>2</sup> Nevertheless, the requirement of an extended healing time to gain adequate levels of bone quality remains a drawback of this procedure.<sup>4-6</sup> Dental implants in the grafted maxillary sinus should be supported largely by the regenerated bone in the augmented area, and so the quality of regeneration in all grafted sinuses may be a major factor for successful results.

However, the quality of regenerated bone in grafted sinus can be affected by the distance to the host bone.<sup>7,8</sup> Since new bone formation originates mainly from the existing alveolar bone at the base of the maxillary sinus, a long time is needed for the regenerated bone to reach to the Schneiderian membrane, which is distant from the osteogenic source.

There have been many attempts at sinus augmentation using the recombinant human bone morphogenetic protein-2 (rhBMP-2) as an osteoinductive factor to accelerate bone regeneration,<sup>9-12</sup> and rhBMP-2 with an absorbable collagen sponge (ACS) was approved for clinical use in sinus augmentation and ridge augmentation by the United States Food and Drug Administration (FDA) in 2007.<sup>13</sup> However, because of its rapid resorption rate and lack of structural durability, the clinical use of the ACS with rhBMP-2 has some limitations in sinus augmentation procedures.<sup>14,15</sup> A

Department of Periodontology, Research Institute for Periodontal Regeneration, Yonsei University College of Dentistry, Seoul, South Korea.  
\*These authors contributed equally to this study.

previous study evaluating the stability of NB in the rabbit sinus after filling with blood clots found that the augmented height was significantly decreased during the early stage of bony regeneration.<sup>16</sup> In another previous study using a rabbit sinus model, rhBMP-2-loaded ACS also resulted in a reduced augmented membrane height in spite of rapid bone regeneration rate.<sup>15</sup> These findings suggest that the space making ability of the ACS is not sufficient for the sinus graft procedure.

Biphasic calcium phosphate (BCP) is a bone substitute material that comprises hydroxyapatite (HA) and  $\beta$ -tricalcium phosphate ( $\beta$ -TCP) in a specific ratio; its space-providing and osteoconductive properties have been well documented.<sup>17–20</sup> BCP has been also used as a carrier for rhBMP-2 in the alveolar ridge defect<sup>21</sup> and spine fusion<sup>22,23</sup> models. Jung *et al.*<sup>24</sup> evaluated rhBMP-2-loaded HA/TCP in the rabbit calvarial onlay model, and concluded that this might be an ideal carrier system for rhBMP-2.

An appropriate degradation rate of biomaterials is a requirement for the ideal carrier/scaffold. The resorption rate of BCP can be controlled by altering the ratio of HA and  $\beta$ -TCP. It has been found that BCP with a high ratio of HA results in successful bone regeneration in various types of osseous defect models.<sup>20,25–27</sup> The HA content of the scaffold can help provide the space for a new bone formation; however, its low biodegradation rate means that the biomaterial could be left unresorbed over a prolonged period of time.<sup>20</sup> In contrast, a higher proportion of  $\beta$ -TCP in BCP increases the resorption rate, and therefore would be replaced more rapidly by NB. Ultimately, the desired outcome is the replacement of grafted biomaterials with natural bone structures containing osteons. Therefore, in the present study, we used BCP with a high  $\beta$ -TCP ratio as the carrier for rhBMP-2.

While soaking of BCP in a solution of rhBMP-2 is an FDA-approved loading method, there are concerns that this may result in uncontrolled flow and uneven distribution of the growth factor.<sup>28</sup> Kim *et al.*<sup>28</sup> introduced the use of BCP coated with *Escherichia coli*-derived rhBMP-2 (ErhBMP-2), which is easy to store and handle at room temperature. In that study, particle- and block-type graft materials loaded with rhBMP-2 using the soaking method exhibited enhanced bone induction in rat calvarial defects.

The purpose of the present study was to (1) elucidate the osteoinductive effect of ErhBMP-2 with the BCP carrier system on the grafted sinus area and surrounding tissues, including the Schneiderian membrane, and (2) to determine the space making ability of BCP in a standardized rabbit sinus model.

## Materials and Methods

### Animals

Thirty-six sinuses of 18 male New Zealand white rabbits weighing 2.5–3 kg were used, including two animals for the *in vitro* test and 16 animals for the *in vivo* test. Animals were housed in separate cages under standard laboratory conditions, with ad libitum access to water and a standard laboratory pellet diet. The animal selection and management, surgical protocol, and preparation followed routines approved by the Institutional Animal Care and Use Committee of Yonsei Medical Center, Seoul, Korea.

### Preparation of ErhBMP-2-coated BCP particles

ErhBMP-2 was provided by the Cowellmedi research institute (Busan, Korea). Microporous BCP (particle type, 0.5–1.0 mm, 70% porosity; Bio-C, Cowellmedi) with a HA: $\beta$ -TCP ratio of 3:7 was used as the ErhBMP-2 carrier. Details of the coating of BCP particles with ErhBMP-2 are available elsewhere.<sup>28</sup> Briefly, the ErhBMP-2 solution (0.67 mL in 1.5 mg/mL buffer) was added to 1 g of BCP particles and lyophilized in a freeze dryer. The solution was frozen by placing the ampoule on precooled shelves and cooling it to  $-43^{\circ}\text{C}$ . The formulations were dried in a condenser at  $-40^{\circ}\text{C}$  (primary drying) and maintained at this temperature for 3 h. They were then placed in a pressure chamber at 5 mTor for 2 h. Secondary drying was performed on a shelf using the following sequence:  $-20^{\circ}\text{C}$  for 4 h,  $-10^{\circ}\text{C}$  for 4 h,  $0^{\circ}\text{C}$  for 2 h, and  $20^{\circ}\text{C}$  for 20 h. The chamber pressure remained constant throughout the procedure.

### In vitro culture

Schneiderian membranes from four normal sinuses of two animals were dissected for the *in vitro* test and washed in DMEM with 10% fetal bovine serum. Membranes were divided into several small pieces ( $3\times 3$  mm) and cultured *in vitro* with the Trowell-type organ culture method in the osteogenic medium (containing  $\alpha$ -MEM with 15% fetal bovine serum, 2 mM L-glutamine, 2 mM  $\beta$ -glycerophosphate, 100 mM L-ascorbic acid 2-phosphate,  $10^{-8}$  dexamethasone, 55 mM 2-mercaptoethanol, 100 U/mL penicillin, and 100 mg/mL streptomycin) with/without ErhBMP-2 (10  $\mu\text{g}$ /mL) for 2 days.

### Quantitative reverse transcriptase-polymerase chain reaction analysis

RNA was extracted from the Schneiderian membrane at 2 days after being incubated in the osteogenic medium *in vitro* with or without the BMP protein (with BMP protein,  $n=8$ ; without BMP protein,  $n=8$ ).

Quantitative reverse transcriptase-polymerase chain reaction (RT-qPCR) was performed using a Thermal Cycler Dice Real-Time System and SYBR Premix EX Taq (Takara, Japan) according to the manufacturer's instructions. PCR amplification was performed with specific primers by using standard protocols; GAPDH forward: 5'-GAGCTGAACGGGA AACTCAC-3', GAPDH reverse: 5'-CACTGTTGAAGTCGCA GGAG-3', osteocalcin (*BGLAP*-like) forward: 5'-AGAGTCT GGCAGAGGCTCA-3', osteocalcin reverse: 5'-CTCGCACACC TCCCTCTT-3', osteopontin (*SPP1*) forward: 5'-GGCTAAA CCCTGACCCATCT-3', osteopontin reverse: 5'-GTGGTCAT CGTCCTCATCCT-3', type I collagen (*COL1A1*) forward: 5'-GGCGATCGTGAGACT-3', type I collagen reverse: 5'-ACCCTGGAGACCGGAGAA-3', alkaline phosphatase (*ALPL*) forward: 5'-CGTGTTCACCTTTGGAGGAT-3', alkaline phosphatase reverse: 5'-TTGTGAGCGTAGTCCACCAT-3', *RUNX2* forward: 5'-CCCTGAACTCTGCACCAAGT-3', *RUNX2* reverse: 5'-GTGCCTCGTGTGGAAGACA-3'. For RT-qPCR, the reaction mixture was initially incubated for 10 s at  $95^{\circ}\text{C}$ . The amplification program comprised 45 cycles of denaturation at  $95^{\circ}\text{C}$  for 5 s, annealing at  $53^{\circ}\text{C}$ – $60^{\circ}\text{C}$  for 20 s, and extension at  $72^{\circ}\text{C}$  for 20 s. The RT-qPCR for each sample was performed in triplicate and the amount of each of the RT-qPCR

products was normalized using GAPDH as an internal control. The data were analyzed with the Thermal Cycler Dice Real-Time System analysis software and the  $2^{-\Delta\Delta Ct}$  method. The statistical calculations were performed using the *t*-test of variables to determine significant changes at the 95% confidence level ( $p < 0.05$ ).

#### *In vivo study design and surgical procedures*

The overall surgical procedure followed the protocol of our previous study.<sup>15</sup> General anesthesia was induced via intramuscular injection, using a mixture of ketamine hydrochloride (Ketalar, Yuhan, Seoul, Korea) and xylazine (Rumpun, Bayer Korea, Seoul, Korea), and local anesthesia was administered with 2% lidocaine (lidocaine HCl, Huons, Seoul, Korea). Following shaving and local disinfection with iodine, a straight incision was made along the midline on the dorsal area of the nasal bone, and a full-thickness flap was elevated laterally to expose the nasal bone. A circular reamer (C-reamer, Neobiotech, Seoul, Korea) with a diameter of 5.5 mm that was designed to minimize membrane perforation was used to prepare the windows bilaterally. The positions of the windows were the same as those determined by Asai *et al.*<sup>29</sup> and Choi *et al.*<sup>15</sup> The prepared bony window was removed and the sinus membrane was carefully elevated. To ensure that the same histologic position was sectioned in each animal, metal pins (Dentium, Seoul, Korea) were inserted on the nasal midline between the prepared windows, at the central-most point of each circular window (Fig. 1).

In each animal, each of the sinuses was randomly allocated to either the ErhBMP-2 or control (BCP alone) group (thus, both the experimental and control groups were represented in each animal). In the ErhBMP-2 group, 0.15 g of graft material (BCP coated with ErhBMP-2) was inserted to the sinus, so that 150  $\mu$ g of ErhBMP-2 was applied. In the contralateral sinus, 0.15 g of uncoated BCP was grafted as a control. After implantation of the graft material, the flap was sutured layer by layer with 4-0 monosyn (glyconate ab-

sorbable monofilament; B-Braun, Aesculap, PA). The animals were sacrificed at 2 weeks ( $n=8$ ) or 8 weeks ( $n=8$ ) postoperatively by an anesthetic overdose.

#### *Radiographic analysis with microcomputed tomography*


Block sections, including the experimental site and the surrounding area were removed and immediately fixed in 10% buffered formalin for 10 days. Microcomputed tomography (micro-CT, Skyscan 1072; Skyscan, Aartselaar, Belgium) images of these block specimens were then taken at a resolution of 35  $\mu$ m (100 kV and 100  $\mu$ A). The scanned CT images were processed in the DICOM format and three-dimensionally reconstructed with PC-based software (On-De-mand3D; Cybermed, Seoul, Korea).

Both sides of the sinuses were visualized using the threshold of 275, as mentioned in previous publications.<sup>30</sup> The augmented area inside of the nasal bone was identified and color coded using the software program; the experimental and control sinuses were colored in red and blue, respectively. The volumes of the colored areas were calculated automatically (in  $\text{mm}^3$ ).

#### *Histologic and histomorphometric analyses*

The rinsed block sections were decalcified in 5% formic acid for 14 days, and then embedded in paraffin. Serial 5- $\mu$ m-thick sections were cut coronally along the center of the window. The two central-most sections were selected from each block, and stained with hematoxylin-eosin and Masson's trichrome. The histologic slides were observed and the images were digitally acquired with the aid of a light microscope (BX50; Olympus, Tokyo, Japan).

Histomorphometric measurements of the captured images were made using a PC-based image analysis system (Image Pro Plus; Media Cybernetics, Silver Spring, MD). The composition of the total augmented sinus was identified, and the relative areas of NB, residual materials (RM), and soft tissue

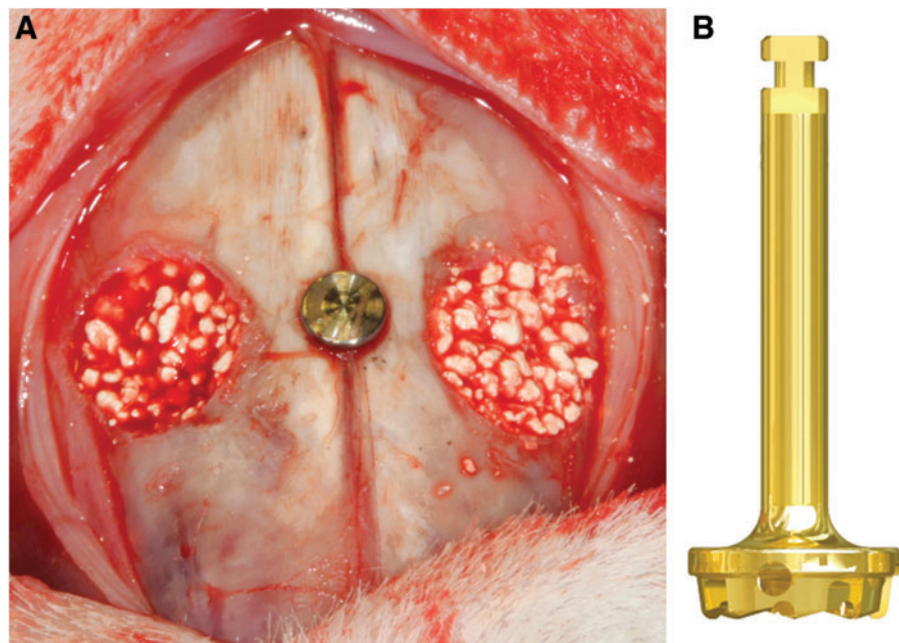


**FIG. 1.** Surgical procedure. **(A)** Windows were prepared bilaterally, and graft materials were inserted. A metal pin was applied to the midline suture to enable identification of the middle of the windows. **(B)** A circular reamer with a diameter of 5.5 mm was used to minimize sinus membrane perforation. Color images available online at [www.liebertpub.com/tea](http://www.liebertpub.com/tea)

(ST) were separately detected and calculated (in  $\text{mm}^2$ ). The total area of the augmented sinus was measured and the proportions (in%) of each composite (i.e., NB, RM, and ST) were obtained. To evaluate the distribution of regenerated bone in the grafted sinus area as a secondary outcome variable, the above-mentioned parameters were measured in specific standardized areas of window, central, and membrane regions. The areas were randomly selected and photomicrographs were taken in original magnification  $\times 200$ . The window region was selected within the grafted area interfacing the imaginary extensions of the pre-existing cortical bone at the margins of the window, and the center region was at the middle of the whole augmented sinus. The membrane region was chosen from just above the Schneiderian membrane. (Fig. 2).

### Statistics

The statistical analysis was performed using a standard software program (SPSS 15.0; SPSS, Chicago, IL). Independent *t*-tests were carried out to compare the results obtained from RT-qPCR in ErhBMP-2-treated and control tissues, and *in vivo* test at 2 and 8 weeks. Paired *t*-tests were used to evaluate the differences between ErhBMP-2-treated and control groups in *in vivo* tests ( $p < 0.05$ ). The data are presented as mean  $\pm$  SD values.

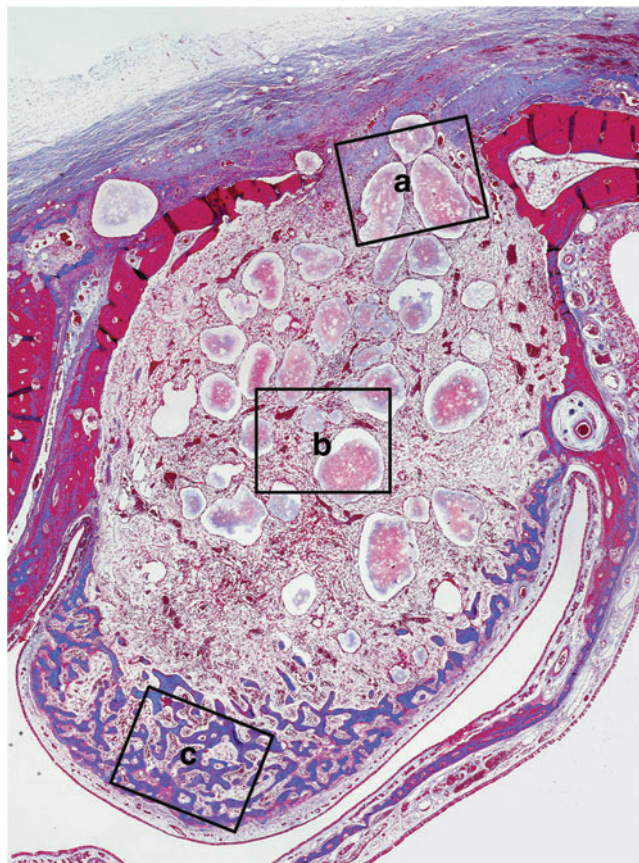

**FIG. 2.** Histomorphometric analysis. The proportions of NB and graft RM were measured on the total augmented area (dotted line), and three randomly selected regions (a, window; b, center; c, membrane). NB, newly formed bone; RM, residual materials. Color images available online at [www.liebertpub.com/tea](http://www.liebertpub.com/tea)

## Results

### Quantitative RT-PCR


Quantitative RT-PCR with RNA extracted from the Schneiderian membrane of adult rabbits showed an extensively increased expression of early osteoblasts, such as *RUNX2*, type I collagen, alkaline phosphatase, and osteopontin. However, the expression level of late osteoblasts like osteocalcin was not significantly changed by BMP. (Fig. 3).

### In vivo test


**Clinical observations.** During the surgical procedure, membrane perforation of less than 1 mm occurred in two sinuses from the 2-week survival group: one in the ErhBMP-2-treated group and the other in the control group. All of the rabbits recovered well and without any adverse healing events such as wound dehiscence or postoperative infection.

### Radiographic analysis: micro-CT

The sinus cavity was filled with radiopaque materials in all groups. Internally, the augmented sinus had a dome shape (Fig. 4A, B). At 2 weeks after surgery, the three-dimensionally reconstructed appearance of the augmented sinuses differed between the experimental and control groups. The spherical shape of the grafted biomaterials was clearly evident in the control group, and the implanted materials resided within high density. In contrast, RM were only sparsely observed in the ErhBMP-2-grafted sinus, and the surfaces of augmented sites exhibited a finely irregular appearance. At 8 weeks of healing, the appearance and surface

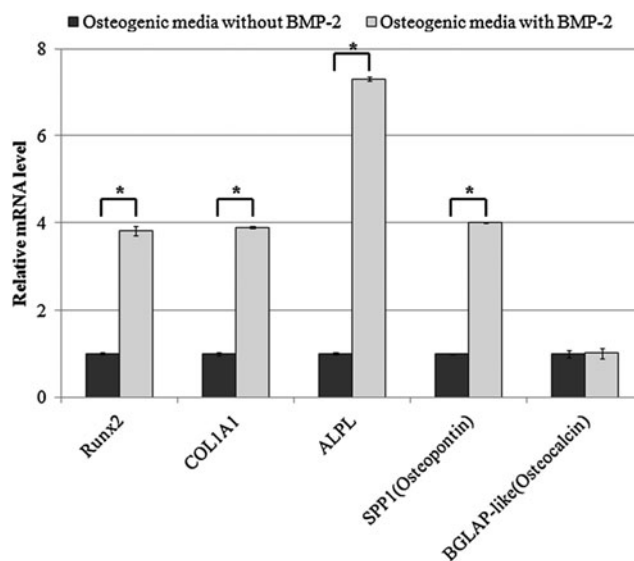

**FIG. 3.** Osteoblastic gene transcriptional changes in the Schneiderian membrane after treatment of *Escherichia coli*-derived rhBMP-2 (ErhBMP-2). Quantitative reverse transcriptase-polymerase chain reaction (RT-qPCR) analysis shows the significant upregulation of *RUNX2*, type I collagen (*COL1A1*), alkaline phosphatase (*ALPL*), and osteopontin (*SPP1*) after treatment of ErhBMP-2 for 48 h (asterisks,  $p < 0.05$ ). The expression level of osteocalcin (*BGLAP*-like) was not evidently changed after ErhBMP-2 treatment. Error bars indicate standard deviations on the normalized ratio.

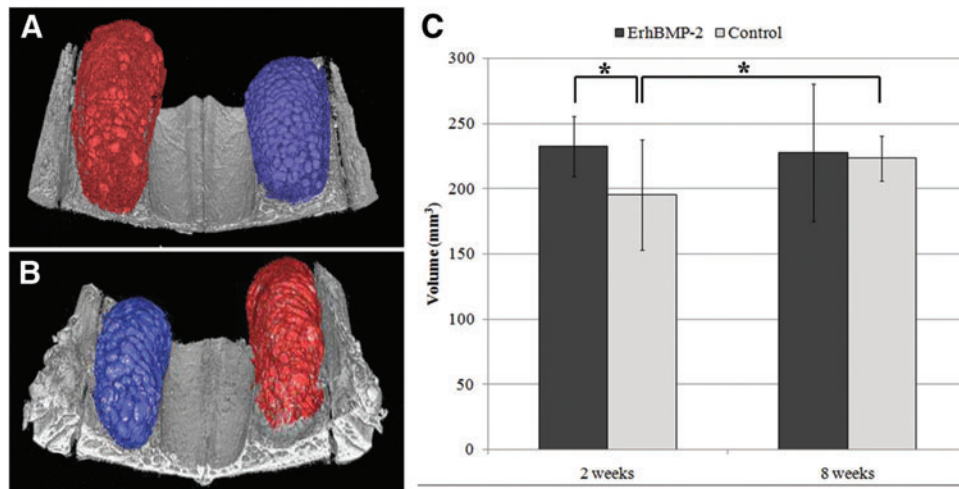


**FIG. 4.** Radiographic analysis. The augmented sinuses were identified and color coded on three-dimensionally reconstructed micro-CT images. The experimental (ErhBMP-2-treated) sinus was coded in red, and the contralateral, control (biphase calcium phosphate [BCP]-alone) sinus was coded in blue. **(A)** After 2 weeks of healing. **(B)** After 8 weeks of healing. **(C)** Total augmented volume. At the 2-week healing point, the total augmented volume was much larger in the ErhBMP-2 group than in the control group ( $*p < 0.001$ ). In the control group, the volume was increased at the 8-week healing point ( $*p = 0.012$ ). Color images available online at [www.liebertpub.com/tea](http://www.liebertpub.com/tea)


of the augmented areas in both the experimental and control sites were similar.

The measured total augmented volume (in  $\text{mm}^3$ ) of each group is shown in Figure 4C. At the 2-week healing point, the volume of the augmented sinus was significantly larger in the ErhBMP-2-treated group ( $232.62 \pm 23.24 \text{ mm}^3$ ) than in the


control group ( $195.29 \pm 42.32 \text{ mm}^3$ ;  $p < 0.001$ ). Conversely, there was no significant difference between the ErhBMP-2 and control groups at the 8-week healing point ( $227.72 \pm 52.59$  vs.  $223.24 \pm 17.37 \text{ mm}^3$ ,  $p = 0.434$ ). The change in dimensions of the experimental sites between the two observation periods was also analyzed. The volume in the control group increased

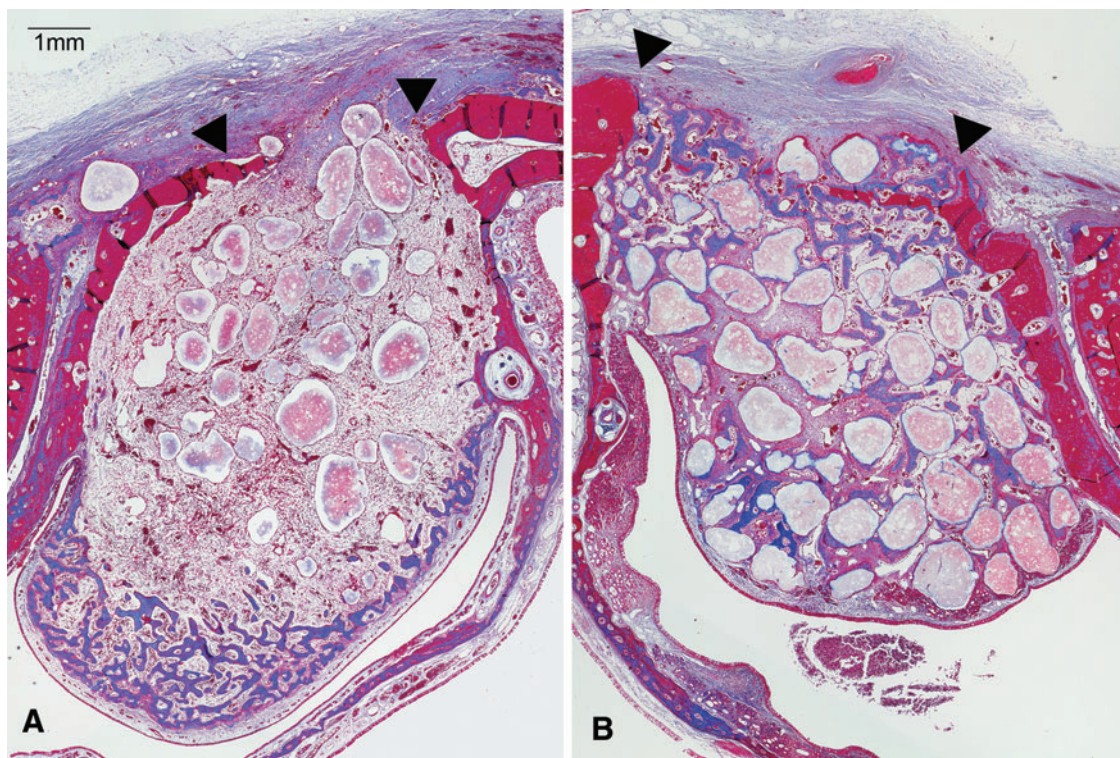


**FIG. 5.** Histologic findings after 2 weeks of healing. NB and RM were seen in both groups. The surgically created windows were clearly distinguished (arrowheads). **(A)** The ErhBMP-2 group. The regenerated bone was found mostly along the sinus membrane. In contrast, there was no bone regeneration in the window and center areas. **(B)** The control group. The NB originating from the native bone was seen throughout the augmented area (Masson trichrome stain). Color images available online at [www.liebertpub.com/tea](http://www.liebertpub.com/tea)

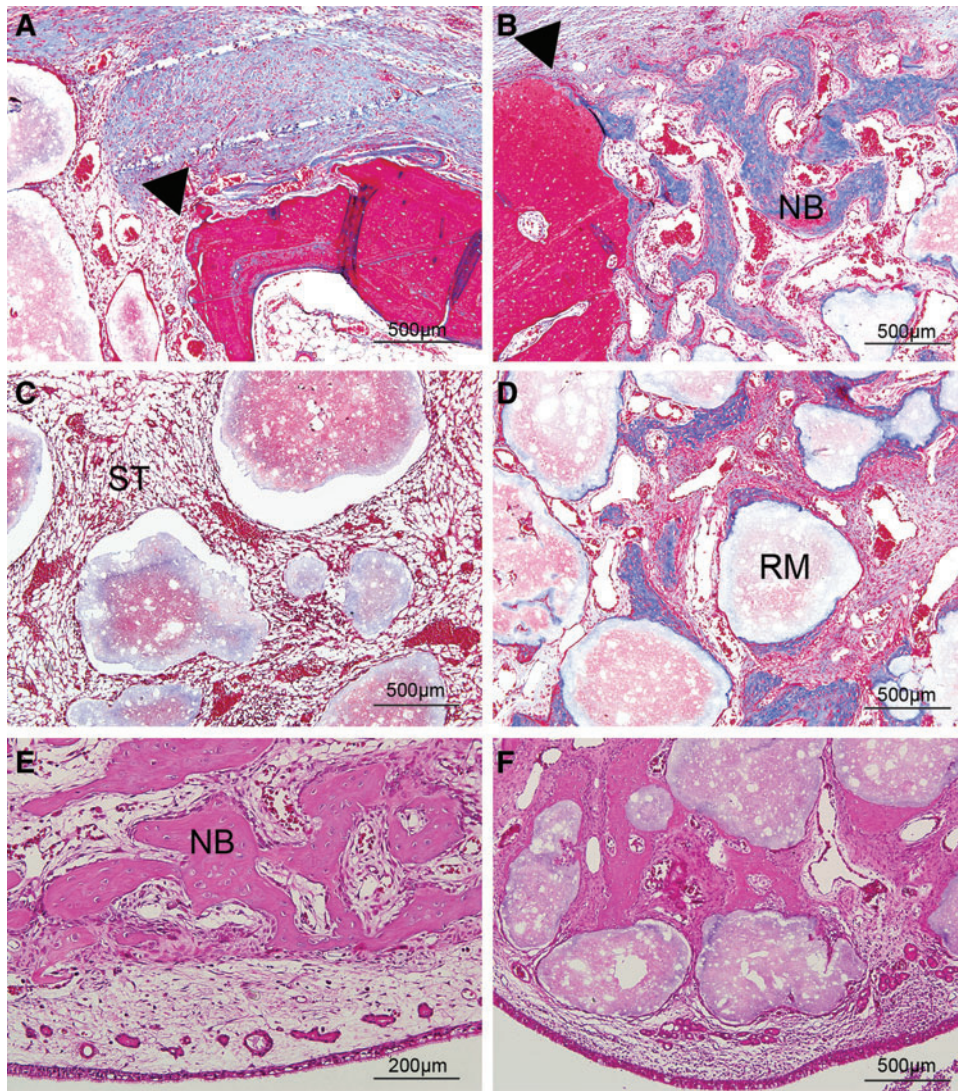

**FIG. 6.** Histologic findings after 2 weeks of healing. The regenerated sinus was divided into three regions: window (A, B), center (C, D), and membrane (E, F). (A, C, E) The ErhBMP-2 group. No bone was found in the window and center regions. On the other hand, respectable bone formation was observed along the Schneiderian membrane without the intervention of BCP materials. (B, D, F) The control group. NB and BCP particles were seen in all regions. A sprouting out of NB was seen, and NB occurred in direct contact with the BCP particles (arrowhead: window site; A–D, Masson’s trichrome; E, F, hematoxylin–eosin). Color images available online at [www.liebertpub.com/tea](http://www.liebertpub.com/tea)

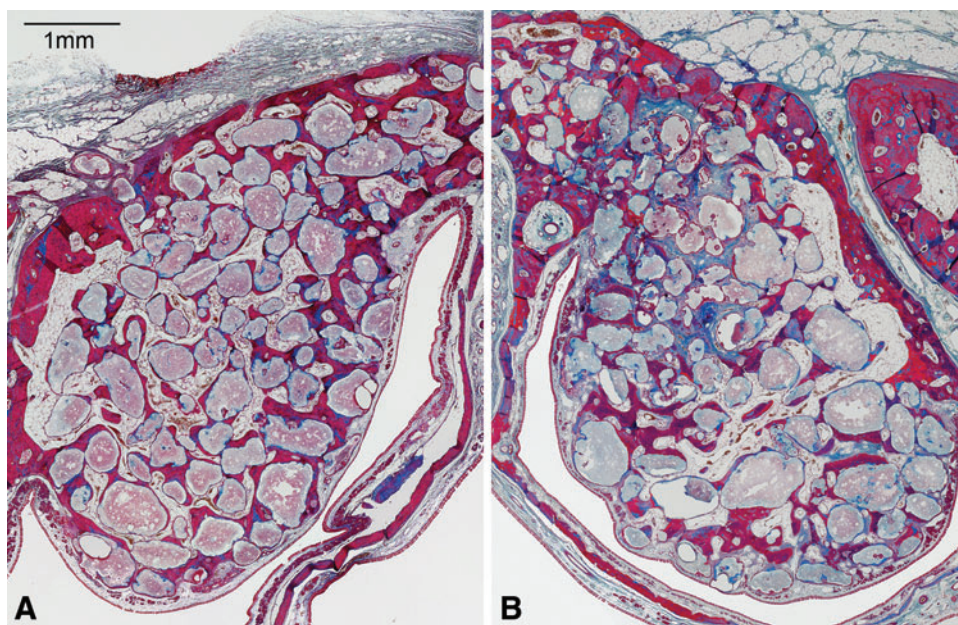

**FIG. 7.** Histologic findings after 8 weeks of healing. The NB was the lamellar bone, and a trabecular pattern was observed. The intertrabecular space was filled with RM, fibrous tissue, and bone marrow. The window area was almost completely closed. (A) The ErhBMP-2 group. (B) The Control group (Masson’s trichrome). Color images available online at [www.liebertpub.com/tea](http://www.liebertpub.com/tea)

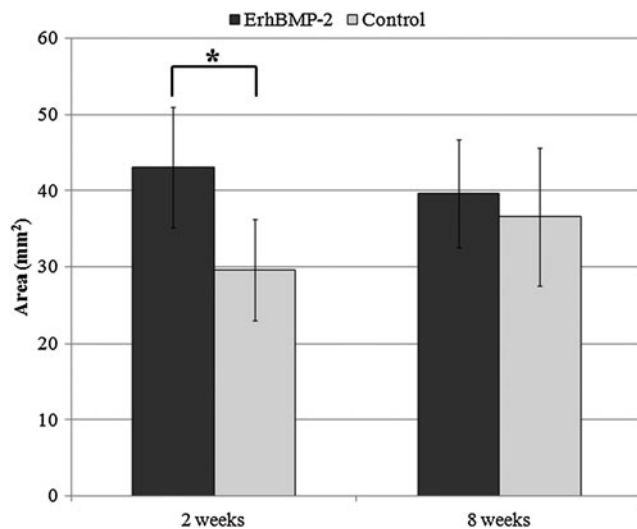

**FIG. 8.** Total area. The total augmented area was larger in the ErhBMP-2 group than in the control group at the 2-week healing point ( $p < 0.001$ ), but did not differ between the two groups at the 8-week point.

significantly as time passed ( $p = 0.012$ ), while there was no significant difference in dimensions in the ErhBMP-2-grafted sinus, although the volume appeared to have slightly decreased at 8 weeks ( $p = 0.06$ ).

#### Histologic observations

NB and RM were seen in both the ErhBMP-2 and control groups at the 2-week healing point (Fig. 5). The cross-sectional shape of the augmented sinus was convex in all animals, and the window area was not yet completely regenerated. The Schneiderian membrane was intact, with no signs of inflammation; numerous serous glands could be seen. The sinus shape in the two rabbits that experienced membrane perforation during the surgical procedure was the same as that in the unperforated rabbits.

Regenerated bone was found mostly near the sinus membrane in the ErhBMP-2 group (Fig. 5A). A trabecular pattern of NB was observed along the Schneiderian membrane and in direct contact with it. In contrast, there was no evidence of regenerated bone in the window and central regions. The RM were sparsely observed, and extensive blood vessels and connective tissues filled in the space between the biomaterials. The remaining BCP particles were irregular in shape with unclear edges (Fig. 6A, C, E).

Regenerated bone was observed all around the augmented area in the control group (Fig. 5B). However, NB was observed more extensively at the area adjacent to the existing alveolar bone rather than along the Schneiderian membrane (Fig. 6B, D, F). NB sprouted out from the lateral surface inside of the augmented sinuses. There were more BCP particles in the sinus sites of the control group than the ErhBMP-2 group. In addition, remnant particles were larger and they were closer to each other at the control sites than at the ErhBMP-2-treated sites.

The two groups exhibited a similar pattern of bone formation and appearance of RM at the 8-week healing point (Fig. 7). The newly formed woven bone was replaced by the

lamellar bone, and a trabecular pattern was observed. The intertrabecular space was filled with RM, fibrovascular tissue, and bone marrow. The window area was almost completely closed with NB, and corticalization between the prepared sites had restored the original curvature of the nasal bone.

#### Histomorphometric analysis

The differences in the total area of augmented sinus (Fig. 8) confirmed the radiographic volumetric analysis. The total augmented area at the 2-week healing point was significantly larger in the ErhBMP-2 group ( $43.02 \pm 7.90 \text{ mm}^2$ ) than in the control group ( $29.64 \pm 6.64 \text{ mm}^2$ ;  $p < 0.001$ ). At the 8-week healing point, this parameter did not differ significantly between the two groups.

The results of the histomorphometric analysis in specific regions are summarized in Figure 9 and Tables 1–4. At the 2-week healing period, the proportions of NB, RM, and ST in the totally augmented area differed between the ErhBMP-2 and control groups (Fig. 9A, Table 1). The proportions of NB and RM were greater in the control group than in the ErhBMP-2 group ( $p = 0.013$  and  $0.002$ , respectively). Likewise, there were significant differences in the relative area of NB between the control and ErhBMP-2 groups in specific regions at the 2-week healing point (Fig. 9B–D, Tables 2–4). Typically, the results in the membrane region of all of the samples were opposite those seen in the window and central regions. Although NB was minimally observed at the window and central regions in ErhBMP-2-grafted sinuses, a significantly increased amount of NB was evident along the Schneiderian membrane of ErhBMP-2-grafted sinuses ( $p = 0.031$ ). At the 8-week healing point, the sinuses of the two groups were filled with similar compositions of NB, RM, and ST.

#### Discussion

ErhBMP-2-coated BCP particles were used in the present study to reinforce the space-making ability and enhance the bone quality in sinus augmentation. Using the ACS carrier for rhBMP-2 accelerated bone regeneration, but a large amount of shrinkage was also observed in the rabbit sinus model.<sup>15</sup> In the present study, the grafted BCP maintained the augmented volume, with excellent NB occurring during the experimental periods. No reduction of the augmented volume was observed; rather, the total volume of sinus was increased in the control group. This finding might be associated with the increased new bone volume being added to the maintained BCP volume. Thus, BCP appears to be a better carrier than ACS with respect to volume maintenance. However, it failed to show the superiority of ErhBMP-2-coated BCP to the control in bone formation. Contrary to our expectation of accelerated bone formation in the experimental group, there was little bone formation around the ErhBMP-2-coated BCP particles at the 2-week healing point.

The differences in healing patterns between the two treatment groups at the early stage are notable. The augmented volume and area were larger in the ErhBMP-2 group than in the control group at the 2-week healing point. These findings were attributed to postoperative swelling at the surgical site. Although many studies have shown that rhBMP-2 has osteoinductive potential, complications such as

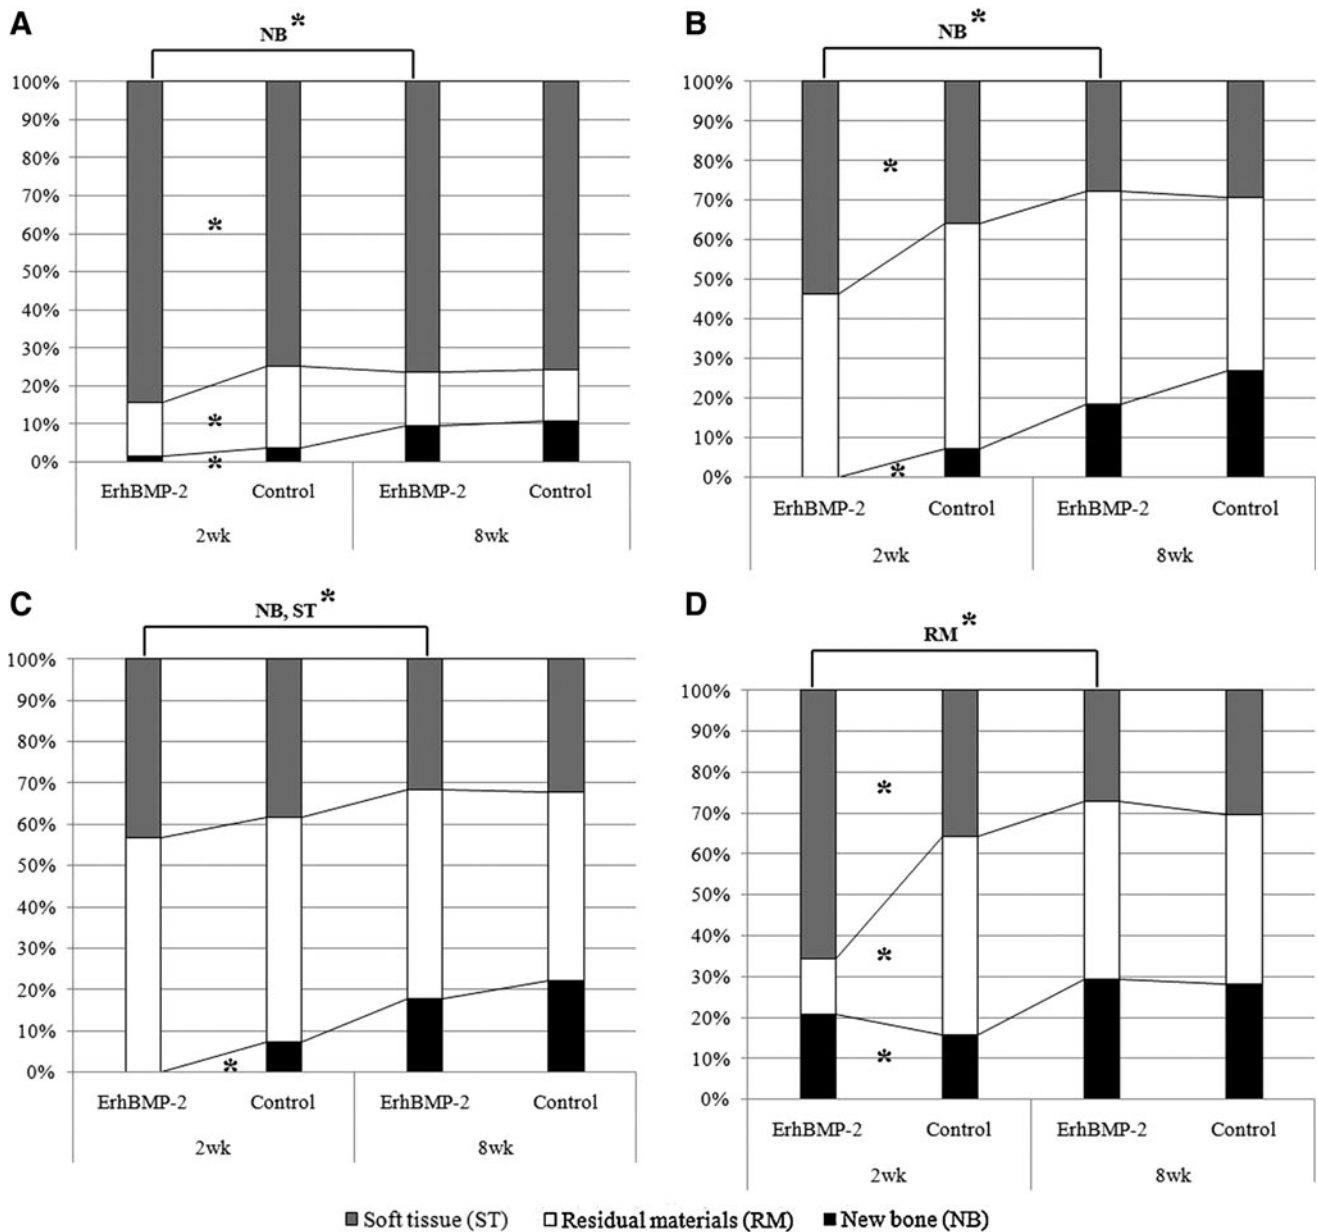


FIG. 9. Fraction of the augmented area. (A) The total area. (B) The window region. (C) The center region. (D) The membrane region. \**p* < 0.05.

TABLE 1. COMPOSITION OF THE TOTAL AUGMENTED AREA (% , MEAN ± SD)

Healing period			NB	RM	ST
2 weeks	ErhBMP-2	Area (mm <sup>2</sup> )	0.74 ± 0.50	6.22 ± 3.30	36.07 ± 5.17
		Ratio (%)	1.63 ± 0.88 <sup>a,b</sup>	13.96 ± 4.96 <sup>b</sup>	84.41 ± 5.15 <sup>b</sup>
	Control	Area (mm <sup>2</sup> )	1.02 ± 0.31	6.55 ± 3.29	22.07 ± 4.90
		Ratio (%)	3.57 ± 1.19	21.53 ± 7.73	74.91 ± 7.25
8 weeks	ErhBMP-2	Area (mm <sup>2</sup> )	2.92 ± 1.01	5.86 ± 2.77	30.79 ± 5.05
		Ratio (%)	9.39 ± 2.21	14.38 ± 5.07	76.23 ± 5.77
	Control	Area (mm <sup>2</sup> )	3.93 ± 1.90	4.73 ± 1.35	27.92 ± 7.79
		Ratio (%)	10.82 ± 4.51	13.35 ± 3.74	75.83 ± 4.49

<sup>a</sup>Significantly different from the group with the same protocol at 8 weeks (*p* < 0.05).

<sup>b</sup>Significantly different from the group with the control group at the same observation period (*p* < 0.05).

NB, newly formed bone; RM, residual materials; ST, soft tissue; ErhBMP-2, *Escherichia coli*-derived rhBMP-2.



TABLE 2. COMPOSITION OF THE WINDOW REGION (% , MEAN  $\pm$  SD)

Healing period	NB	RM	ST
2 weeks			
ErhBMP-2	0.06 $\pm$ 0.18 <sup>a,b</sup>	46.18 $\pm$ 15.38	53.75 $\pm$ 15.75 <sup>b</sup>
Control	7.27 $\pm$ 5.09	56.78 $\pm$ 6.74	35.95 $\pm$ 3.89
8 weeks			
ErhBMP-2	19.97 $\pm$ 5.58	52.74 $\pm$ 9.98	27.29 $\pm$ 7.27
Control	26.81 $\pm$ 10.42	43.81 $\pm$ 7.10	29.37 $\pm$ 5.71

<sup>a</sup>Significantly different from the group with the same protocol at 8 weeks ( $p < 0.05$ ).

<sup>b</sup>Significantly different from the group with the control group at the same observation period ( $p < 0.05$ ).

postoperative swelling have also been reported.<sup>31-33</sup> The amount of swelling is thought to depend upon the total dose of rhBMP-2 delivered to the surgical site.<sup>31</sup>

Our histologic and histomorphometric analyses revealed specific atypical features in the ErhBMP-2 group at the 2-week healing point. Little NB was found around the lateral bony wall and the grafted BCP, while most of the NB was formed along the reflected Schneiderian membrane without the intervention of BCP particles. On the other hand, newly formed trabecular bone projected from the lateral bone to the center of the sinus in the control group, and was in direct contact with the grafted BCP particles near to the parent bone. The orientation of bone healing appeared to differ between the two groups.

Some researchers have proposed that the Schneiderian membrane contains osteogenic progenitor cells, and that bone regeneration originates from the sinus membrane.<sup>34-36</sup> Srouji *et al.*<sup>34</sup> evaluated the cells derived from the human maxillary sinus membrane, and found that these cells were positive for mesenchymal stem cell markers, and underwent osteogenic differentiation both *in vitro* and *in vivo*. However, another recent *in vivo* study revealed limited influence of the Schneiderian membrane on bone formation after sinus floor elevation.<sup>37</sup> The results of the present study could support these two opposite studies, which showed different healing patterns around the Schneiderian membrane in ErhBMP-2-treated and control sites. A seam of NB was found along the Schneiderian membrane in the experimental group of the present study, even at 2 weeks. Results from RT-qPCR also showed increased expression of early osteoblasts, such as

TABLE 3. COMPOSITION OF THE CENTER REGION (% , MEAN  $\pm$  SD)

Healing period	NB	RM	ST
2 weeks			
ErhBMP-2	0 <sup>a,b</sup>	56.82 $\pm$ 7.27	43.18 $\pm$ 7.27 <sup>a</sup>
Control	7.41 $\pm$ 5.21	54.35 $\pm$ 6.39	38.24 $\pm$ 7.55
8 weeks			
ErhBMP-2	17.69 $\pm$ 6.83	50.63 $\pm$ 7.84	31.68 $\pm$ 2.39
Control	22.14 $\pm$ 7.83	45.73 $\pm$ 7.73	32.12 $\pm$ 9.49

<sup>a</sup>Significantly different from the group with the same protocol at 8 weeks ( $p < 0.05$ ).

<sup>b</sup>Significantly different from the group with the control group at the same observation period ( $p < 0.05$ ).

TABLE 4. COMPOSITION OF MEMBRANE REGION (% , MEAN  $\pm$  SD)

Healing period	NB	RM	ST
2 weeks			
ErhBMP-2	20.86 $\pm$ 12.05 <sup>a</sup>	13.38 $\pm$ 11.03 <sup>a,b</sup>	65.76 $\pm$ 8.40 <sup>a</sup>
Control	15.58 $\pm$ 4.33	48.76 $\pm$ 7.46	35.65 $\pm$ 6.06
8 weeks			
ErhBMP-2	29.33 $\pm$ 12.05	43.67 $\pm$ 5.76	27.00 $\pm$ 5.50
Control	28.17 $\pm$ 7.94	41.42 $\pm$ 12.63	30.40 $\pm$ 7.01

<sup>a</sup>Significantly different from the group with the control group at the same observation period ( $p < 0.05$ ).

<sup>b</sup>Significantly different from the group with the same protocol at 8 weeks ( $p < 0.05$ ).

*RUNX2*, type I collagen, alkaline phosphatase, and osteopontin. It can be assumed that ErhBMP-2 might provoke osteogenic differentiation of progenitor cells of the Schneiderian membrane in the early healing phase. From the clinical point of view, early corticalization of the outer sinus surface could protect the augmented space from the volume shrinkage by remodeling or the pressure during respiration. Therefore, it may provide a suitable environment for increasing the bone formation throughout the grafted area.

On the other hand, most bone substitute materials such as BCP are osteoconductive materials that cannot induce a new bone formation on their own. The trabecular bone sprouted mainly from the lateral bony wall in the control group, and less bone formation was observed around the Schneiderian membrane in the control group compared with the experimental group.

The experimental and control groups showed similar results at 8 weeks, unlike at 2 weeks, where a significant difference between the two groups was shown. The remaining materials were rather increased in the membrane region of the ErhBMP-2 group compared to 2 weeks. It can be assumed that the new bone layer formed in the early stage in the membrane region has been resorbed due to pneumatization caused by air pressure during the remodeling process. Nevertheless, the total augmented volume was only slightly decreased because of the space-making ability of BCP particles. This suggests that the ratio of remaining particles might be higher at 8 weeks in the ErhBMP-2 group.

Our results demonstrate an osteoinductive effect of ErhBMP-2 in the membrane region, but the total amount of NB was less in the ErhBMP-2 group than in the control group at the 2-week healing point, although it was similar at 8 weeks. In contrast to the membrane region, the center region of the experimental group was filled mainly with the connective tissue and carrier materials. There were many blood vessels, and the density of particles was lower than that in the control group. RhBMP-2 is known to induce both angiogenesis and osteogenesis, through chemotaxis of osteoblasts and endothelial cells.<sup>38</sup> It is inferred that swelling by angiogenesis and chemotaxis of rhBMP-2 may have resulted in the relatively sparse presence of the particles.

It is unclear why the new bone formation did not occur around the graft particles in the experimental group at 2 weeks. One possibility is that the high dose of rhBMP-2 impaired healing. The effective dose of BMP-2 is known to differ between species and in various types of animal

models. In general, a much smaller amount of rhBMP-2 is sufficient to induce bone formation in small animals such as rabbits than in human beings. BCP particles coated with 1.5 mg/mL of the ErhBMP-2 solution were grafted in this study; it is possible that this constitutes an overdose in rabbits. Zara *et al.*<sup>33</sup> reported on the adverse effects of high-dose BMP-2. They found that BMP-2 had dose-dependent side effects, such as cyst-like bone void formation. In the present study, it can be assumed that the membrane region spatially distant from the particles was stimulated by the diluted signal of the released rhBMP-2, while osteogenic differentiation was inhibited at the area near to the particle due to the high concentration of rhBMP-2. The other possibility is that the method used to load the rhBMP-2 molecule onto the BCP particles in the present study—whereby the rhBMP-2 solution was lyophilized to the BCP particle surface—or the process of its release altered the biological activity of the rhBMP-2 molecules. Further study is required to clarify these potentially adverse effects.

### Conclusion

Within the limitations of the study, it can be concluded that BCP exhibits good space maintenance in sinus augmentation, and that ErhBMP-2 may stimulate the osteoinductive potential of the sinus membrane at the early stage of healing, although there was no significant superiority in ultimate bone formation.

### Acknowledgment

This research was supported by a Basic Science Research Program through the National Research Foundation of Korea (NRF), funded by the Ministry of Education, Science, and Technology (no. 2011-0007795).

### Disclosure Statement

No competing financial interests exist.

### References

- Wallace, S.S., and Froum, S.J. Effect of maxillary sinus augmentation on the survival of endosseous dental implants. A systematic review. *Ann Periodontol* **8**, 328, 2003.
- Del Fabbro, M., Rosano, G., and Taschieri, S. Implant survival rates after maxillary sinus augmentation. *Eur J Oral Sci* **116**, 497, 2008.
- Pjetursson, B.E., Tan, W.C., Zwahlen, M., and Lang, N.P. A systematic review of the success of sinus floor elevation and survival of implants inserted in combination with sinus floor elevation. *J Clin Periodontol* **35**, 216, 2008.
- Nishibori, M., Betts, N.J., Salama, H., and Listgarten, M.A. Short-term healing of autogenous and allogeneic bone grafts after sinus augmentation: a report of 2 cases. *J Periodontol* **65**, 958, 1994.
- Wallace, S.S., Froum, S.J., and Tarnow, D.P. Histologic evaluation of a sinus elevation procedure: a clinical report. *Int J Periodontics Restorative Dent* **16**, 46, 1996.
- Lorenzetti, M., Mozzati, M., Campanino, P.P., and Valente, G. Bone augmentation of the inferior floor of the maxillary sinus with autogenous bone or composite bone grafts: a histologic-histomorphometric preliminary report. *Int J Oral Maxillofac Implants* **13**, 69, 1998.
- Tadjoedin, E.S., de Lange, G.L., Bronckers, A.L., Lyaruu, D.M., and Burger, E.H. Deproteinized cancellous bovine bone (Bio-Oss) as bone substitute for sinus floor elevation. A retrospective, histomorphometrical study of five cases. *J Clin Periodontol* **30**, 261, 2003.
- Busenlechner, D., Huber, C.D., Vasak, C., Dobsak, A., Gruber, R., and Watzek, G. Sinus augmentation analysis revised: the gradient of graft consolidation. *Clin Oral Implants Res* **20**, 1078, 2009.
- Boyne, P.J., Lilly, L.C., Marx, R.E., Moy, P.K., Nevins, M., Spagnoli, D.B., and Triplett, R.G. *De novo* bone induction by recombinant human bone morphogenetic protein-2 (rhBMP-2) in maxillary sinus floor augmentation. *J Oral Maxillofac Surg* **63**, 1693, 2005.
- Jiang, X.Q., Sun, X.J., Lai, H.C., Zhao, J., Wang, S.Y., and Zhang, Z.Y. Maxillary sinus floor elevation using a tissue-engineered bone complex with beta-TCP and BMP-2 gene-modified bMSCs in rabbits. *Clin Oral Implants Res* **20**, 1333, 2009.
- Xia, L., Xu, Y., Chang, Q., Sun, X., Zeng, D., Zhang, W., Zhang, X., Zhang, Z., and Jiang, X. Maxillary sinus floor elevation using BMP-2 and Nell-1 gene-modified bone marrow stromal cells and TCP in rabbits. *Calcif Tissue Int* **89**, 53, 2011.
- Zhang, W., Wang, X., Wang, S., Zhao, J., Xu, L., Zhu, C., Zeng, D., Chen, J., Zhang, Z., Kaplan, D.L., and Jiang, X. The use of injectable sonication-induced silk hydrogel for VEGF(165) and BMP-2 delivery for elevation of the maxillary sinus floor. *Biomaterials* **32**, 9415, 2011.
- Tarnow, D.P., Wallace, S.S., Testori, T., Froum, S.J., Motroni, A., and Prasad, H.S. Maxillary sinus augmentation using recombinant bone morphogenetic protein-2/acellular collagen sponge in combination with a mineralized bone replacement graft: a report of three cases. *Int J Periodontics Restorative Dent* **30**, 139, 2010.
- Barboza, E.P., Duarte, M.E., Geolas, L., Sorensen, R.G., Riedel, G.E., and Wikesjo, U.M. Ridge augmentation following implantation of recombinant human bone morphogenetic protein-2 in the dog. *J Periodontol* **71**, 488, 2000.
- Choi, Y., Yun, J.H., Kim, C.S., Choi, S.H., Chai, J.K., and Jung, U.W. Sinus augmentation using absorbable collagen sponge loaded with *Escherichia coli*-expressed recombinant human bone morphogenetic protein 2 in a standardized rabbit sinus model: a radiographic and histologic analysis. *Clin Oral Implants Res* **23**, 682, 2012.
- Xu, H., Shimizu, Y., and Ooya, K. Histomorphometric study of the stability of newly formed bone after elevation of the floor of the maxillary sinus. *Br J Oral Maxillofac Surg* **43**, 493, 2005.
- Fellah, B.H., Gauthier, O., Weiss, P., Chappard, D., and Layrolle, P. Osteogenicity of biphasic calcium phosphate ceramics and bone autograft in a goat model. *Biomaterials* **29**, 1177, 2008.
- Froum, S.J., Wallace, S.S., Cho, S.C., Elian, N., and Tarnow, D.P. Histomorphometric comparison of a biphasic bone ceramic to anorganic bovine bone for sinus augmentation: 6- to 8-month postsurgical assessment of vital bone formation. A pilot study. *Int J Periodontics Restorative Dent* **28**, 273, 2008.
- Fleckenstein, K.B., Cuenin, M.F., Peacock, M.E., Billman, M.A., Swiec, G.D., Buxton, T.B., Singh, B.B., and McPherson, J.C., 3rd. Effect of a hydroxyapatite tricalcium phosphate alloplast on osseous repair in the rat calvarium. *J Periodontol* **77**, 39, 2006.
- Lee, J.H., Jung, U.W., Kim, C.S., Choi, S.H., and Cho, K.S. Histologic and clinical evaluation for maxillary sinus aug-

- mentation using macroporous biphasic calcium phosphate in human. *Clin Oral Implants Res* **19**, 767, 2008.
21. Miranda, D.A., Blumenthal, N.M., Sorensen, R.G., Wozney, J.M., and Wikesjo, U.M. Evaluation of recombinant human bone morphogenetic protein-2 on the repair of alveolar ridge defects in baboons. *J Periodontol* **76**, 210, 2005.
  22. Boden, S.D., Martin, G.J., Jr., Morone, M.A., Ugbo, J.L., and Moskovitz, P.A. Posterolateral lumbar intertransverse process spine arthrodesis with recombinant human bone morphogenetic protein 2/hydroxyapatite-tricalcium phosphate after laminectomy in the nonhuman primate. *Spine (Phila Pa 1976)* **24**, 1179, 1999.
  23. Minamide, A., Kawakami, M., Hashizume, H., Sakata, R., and Tamaki, T. Evaluation of carriers of bone morphogenetic protein for spinal fusion. *Spine (Phila Pa 1976)* **26**, 933, 2001.
  24. Jung, R.E., Weber, F.E., Thoma, D.S., Ehrbar, M., Cochran, D.L., and Hammerle, C.H. Bone morphogenetic protein-2 enhances bone formation when delivered by a synthetic matrix containing hydroxyapatite/tricalciumphosphate. *Clin Oral Implants Res* **19**, 188, 2008.
  25. Nery, E.B., LeGeros, R.Z., Lynch, K.L., and Lee, K. Tissue response to biphasic calcium phosphate ceramic with different ratios of HA/beta TCP in periodontal osseous defects. *J Periodontol* **63**, 729, 1992.
  26. Ellinger, R.F., Nery, E.B., and Lynch, K.L. Histological assessment of periodontal osseous defects following implantation of hydroxyapatite and biphasic calcium phosphate ceramics: a case report. *Int J Periodontics Restorative Dent* **6**, 22, 1986.
  27. Cha, J.K., Park, J.C., Jung, U.W., Kim, C.S., Cho, K.S., and Choi, S.H. Case series of maxillary sinus augmentation with biphasic calcium phosphate: a clinical and radiographic study. *J Periodontal Implant Sci* **41**, 98, 2011.
  28. Kim, J.W., Choi, K.H., Yun, J.H., Jung, U.W., Kim, C.S., Choi, S.H., and Cho, K.S. Bone formation of block and particulated biphasic calcium phosphate lyophilized with *Escherichia coli*-derived recombinant human bone morphogenetic protein 2 in rat calvarial defects. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* **112**, 298, 2011.
  29. Asai, S., Shimizu, Y., and Ooya, K. Maxillary sinus augmentation model in rabbits: effect of occluded nasal ostium on new bone formation. *Clin Oral Implants Res* **13**, 405, 2002.
  30. Aghaloo, T., Cowan, C.M., Chou, Y.F., Zhang, X., Lee, H., Miao, S., Hong, N., Kuroda, S., Wu, B., Ting, K., and Soo, C. Nell-1-induced bone regeneration in calvarial defects. *Am J Pathol* **169**, 903, 2006.
  31. Smucker, J.D., Rhee, J.M., Singh, K., Yoon, S.T., and Heller, J.G. Increased swelling complications associated with off-label usage of rhBMP-2 in the anterior cervical spine. *Spine (Phila Pa 1976)* **31**, 2813, 2006.
  32. Shahlaie, K., and Kim, K.D. Occipitocervical fusion using recombinant human bone morphogenetic protein-2: adverse effects due to tissue swelling and seroma. *Spine (Phila Pa 1976)* **33**, 2361, 2008.
  33. Zara, J.N., Siu, R.K., Zhang, X., Shen, J., Ngo, R., Lee, M., Li, W., Chiang, M., Chung, J., Kwak, J., Wu, B.M., Ting, K., and Soo, C. High doses of bone morphogenetic protein 2 induce structurally abnormal bone and inflammation *in vivo*. *Tissue Eng Part A* **17**, 1389, 2011.
  34. Srouji, S., Kizhner, T., Ben David, D., Riminucci, M., Bianco, P., and Livne, E. The Schneiderian membrane contains osteoprogenitor cells: *in vivo* and *in vitro* study. *Calcif Tissue Int* **84**, 138, 2009.
  35. Kim, S.W., Lee, I.K., Yun, K.I., Kim, C.H., and Park, J.U. Adult stem cells derived from human maxillary sinus membrane and their osteogenic differentiation. *Int J Oral Maxillofac Implants* **24**, 991, 2009.
  36. Gruber, R., Kandler, B., Fuerst, G., Fischer, M.B., and Watzek, G. Porcine sinus mucosa holds cells that respond to bone morphogenetic protein (BMP)-6 and BMP-7 with increased osteogenic differentiation *in vitro*. *Clin Oral Implants Res* **15**, 575, 2004.
  37. Scala, A., Botticelli, D., Faeda, R.S., Garcia Rangel, I., Jr., Americo de Oliveira, J., and Lang, N.P. Lack of influence of the Schneiderian membrane in forming new bone apical to implants simultaneously installed with sinus floor elevation: an experimental study in monkeys. *Clin Oral Implants Res* **23**, 175, 2012.
  38. Li, G., Cui, Y., McMurray, L., Allen, W.E., and Wang, H. rhBMP-2, rhVEGF(165), rhPTN and thrombin-related peptide, TP508 induce chemotaxis of human osteoblasts and microvascular endothelial cells. *J Orthop Res* **23**, 680, 2005.

Address correspondence to:

Ui-Won Jung, PhD

Department of Periodontology

Research Institute for Periodontal Regeneration

Yonsei University College of Dentistry

50 Yonsei-ro, Seodaemun-gu

Seoul 120-752

South Korea

E-mail: drjew@yuhs.ac

Received: December 6, 2012

Accepted: March 26, 2013

Online Publication Date: May 10, 2013